



# SPS 6

**Special Products Standard  
for Structural Face-Glued Lumber**



May 2026





# **SPS 6**

## **SPECIAL PRODUCTS STANDARD**

### **FOR**

## **STRUCTURAL FACE-GLUED LUMBER**

**EFFECTIVE: May 1, 2026**

**Supersedes all Previous Editions, Revisions and Supplements**

**Approved by the Canadian Lumber Standards Accreditation Board – March 27, 2026**

**Approved by the American Lumber Standard Committee, Board of Review  
as complying with the ALSC Glued Lumber Policy – April 10, 2026**

Published by the

**NATIONAL LUMBER GRADES AUTHORITY**

Ottawa, ON, Canada

[www.nlga.org](http://www.nlga.org)

**© NATIONAL LUMBER GRADES AUTHORITY – 2004, 2005, 2010, 2015, 2026**

**“All rights reserved.”** No part of this publication may be reproduced or stored in any material form (including photocopying, storing it in any medium by electronic means whether or not transiently or incidentally to such use of this publication) without the written permission of the copyright holder except in accordance with the provisions of the **Copyright Act**. Applications for the copyright holder’s written permission to produce any part of this publication must be addressed to the copyright holder.

**Warning:** The doing of any unauthorized act in relation to a copyrighted work may result in both civil claim for damages and criminal prosecution.



**TABLE OF CONTENTS**

<b>PREFACE</b> .....	<b>5</b>
<b>1.0 SCOPE</b> .....	<b>6</b>
1.1 PART A AND PART B .....	6
1.2 NLGA STANDARD GRADING RULES.....	6
1.3 UNITS .....	6
1.4 DESIGN VALUES .....	6
1.5 STRUCTURAL FACE-GLUED LUMBER REQUIREMENTS.....	6
1.6 INTERPRETATIONS .....	6
<b>2.0 DEFINITIONS AND REFERENCED PUBLICATIONS</b> .....	<b>6</b>
2.1 DEFINITIONS .....	6
2.2 REFERENCED PUBLICATIONS .....	8
<b>PART A - PRODUCT SPECIFICATIONS FOR STRUCTURAL FACE-GLUED LUMBER</b> .....	<b>9</b>
<b>3.0 PRODUCT DESCRIPTION</b> .....	<b>9</b>
3.1 APPLICATIONS AND INTERCHANGEABILITY .....	9
3.2 DEMONSTRATION OF CONFORMANCE.....	9
3.3 SPECIAL APPLICATIONS .....	9
<b>4.0 GRADE DESCRIPTION</b> .....	<b>10</b>
<b>5.0 STANDARD SIZES</b> .....	<b>10</b>
<b>6.0 LUMBER COMPONENT REQUIREMENTS</b> .....	<b>10</b>
6.1 SPECIES .....	10
6.2 LUMBER COMPONENTS .....	10
6.3 FINISHED PRODUCT LUMBER QUALITY .....	11
<b>7.0 ADHESIVE REQUIREMENTS</b> .....	<b>11</b>
7.1 ADHESIVE SPECIFICATION .....	11
7.2 SEPARATE APPLICATION ADHESIVES .....	11
7.3 ADHESIVE MIXING.....	11
7.4 BONDED SURFACE FABRICATION.....	11
<b>8.0 PROPERTY REQUIREMENTS FOR STRUCTURAL FACE-GLUED LUMBER</b> .....	<b>11</b>
8.1 MODULUS OF RUPTURE (MOR).....	11
8.2 SHEAR STRENGTH PARALLEL TO GRAIN (Fv).....	12
8.3 WOOD FAILURE .....	12
8.4 FINAL GRADE .....	12
<b>9.0 STRUCTURAL FACE-GLUED LUMBER PROPERTY EVALUATION PROCEDURES</b> .....	<b>14</b>
9.1 MODULUS OF RUPTURE (MOR).....	14
9.2 SHEAR STRENGTH PARALLEL TO GRAIN (Fv).....	14
9.3 ENVIRONMENTAL CONDITIONS .....	14
<b>10.0 GRADE STAMPING OF STRUCTURAL FACE-GLUED LUMBER</b> .....	<b>15</b>
10.1 GENERAL.....	15
10.2 GRADE STAMP REQUIREMENTS .....	15
<b>PART B - QUALIFICATION AND QUALITY CONTROL REQUIREMENTS</b> .....	<b>15</b>
<b>11.0 EQUIPMENT</b> .....	<b>15</b>
11.1 MOR TEST EQUIPMENT .....	15
11.2 SHEAR PARALLEL TO GRAIN TEST EQUIPMENT .....	15
11.3 PRESSURE-VACUUM-DRY TREATMENT EQUIPMENT .....	15
<b>12.0 QUALITY CONTROL MANUAL</b> .....	<b>16</b>
12.1 GENERAL.....	16
12.2 PREPARATION, REVISION AND APPROVAL.....	16
12.3 CONTENTS.....	16
<b>13.0 QUALIFICATION REQUIREMENTS</b> .....	<b>17</b>
13.1 INITIAL FACILITY QUALIFICATION .....	17
13.2 NEW PRODUCTION LINE START-UP OR MAJOR CHANGE REQUIREMENTS (TO BE PERFORMED BY THE FACILITY).....	17
13.3 INITIAL QUALIFICATION SAMPLING (TO BE PERFORMED BY THE AGENCY) .....	17
13.4 RE-QUALIFICATION SAMPLING .....	18
13.5 DECISION RULES.....	18
13.6 SUBSEQUENT QUALIFICATION .....	19
13.7 NON-PRODUCTION OF STRUCTURAL FACE-GLUED LUMBER .....	19
<b>14.0 EQUIPMENT CALIBRATION</b> .....	<b>19</b>
14.1 TEST EQUIPMENT AND SPOT-CHECK DEVICES .....	19
14.2 CALIBRATION DEVICES .....	19
14.3 INDEPENDENT CALIBRATION LABORATORY REPORTING REQUIREMENTS .....	20
<b>15.0 QUALITY CONTROL REQUIREMENTS</b> .....	<b>20</b>
15.1 QUALITY CONTROL PROCEDURES .....	20
15.2 QUALITY CONTROL SAMPLING.....	20

15.3 QUALITY CONTROL TESTING ..... 20  
 15.4 ANALYSIS OF QUALITY CONTROL TESTS ..... 20  
 15.5 IDENTIFICATION AND TRACEABILITY ..... 21  
 15.6 QUALITY CONTROL RECORDS ..... 21  
**16.0 REINSPECTION PROVISIONS ..... 22**  
 16.1 GENERAL ..... 22  
 16.2 BENDING STRENGTH AND/OR SHEAR STRENGTH PARALLEL TO GRAIN SAMPLING AND EVALUATION ..... 22  
**APPENDICES (INFORMATIVE) ..... 23**

**APPENDICES**

APPENDIX I – EXAMPLES OF LUMBER CROSS-SECTIONS FALLING WITHIN THE SCOPE OF SPS 6..... 23  
 APPENDIX II – MOR SPAN-TO-DEPTH ADJUSTMENT FACTORS ..... 24  
 APPENDIX III –SHEAR BLOCK TEST SPECIMEN DIMENSIONS..... 24  
 APPENDIX IV – PRESSURE-VACUUM-DRY TREATMENT ..... 25  
 APPENDIX V – COMMENTARY ON QUALITY CONTROL MANUAL CONTENTS..... 25  
 APPENDIX VI – COMMENTARY ON WOOD FAILURE ASSESSMENT ..... 25  
 APPENDIX VII – FLOW CHART FOR “OUT-OF-CONTROL” IN BENDING STRENGTH..... 26  
 APPENDIX VIII – FLOW CHART FOR “OUT-OF-CONTROL” IN SHEAR STRENGTH PARALLEL TO GRAIN AND/OR WOOD FAILURE ..... 27  
 APPENDIX IX – AGENCY ADMINISTRATION ..... 28

**LIST OF FIGURES**

FIGURE 1 - EXAMPLES OF STRUCTURAL FACE-GLUED LUMBER PRODUCT CROSS-SECTIONS ..... 23  
 FIGURE 2 - TEST SPECIMEN SHEAR BLOCK AND SAW KERF DIMENSIONS..... 24  
 FIGURE 3 - BENDING STRENGTH FAILURE RE-QUALIFICATION FLOW CHART ..... 26  
 FIGURE 4 - SHEAR STRENGTH PARALLEL TO GRAIN AND/OR WOOD FAILURE RE-QUALIFICATION FLOW CHART..... 27

**LIST OF TABLES**

TABLE 1 - STANDARD THICKNESSES AND WIDTHS (AS SPECIFIED IN CSA O141 AND PS 20) ..... 10  
 TABLE 2 – PROPERTY TEST VALUES FOR STRUCTURAL FACE-GLUED LUMBER ..... 13  
 TABLE 3 - TEST EQUIPMENT SPOT-CHECK FREQUENCY ..... 19  
 TABLE 4 - CORRECTION FACTORS FOR EDGE BENDING MOR ..... 24

## PREFACE

This NLGA Special Products Standard for Structural Face-Glued Lumber (SPS 6) consists of 28 pages.

This Standard, like all NLGA Standards, is subject to periodic review and may be amended from time to time. To identify or obtain the most current version of NLGA - SPS 6, or any associated Supplements or Errata, check the publication section of the NLGA website at [www.nlga.org](http://www.nlga.org).

The following is a chronological summary of SPS 6 revisions since December 2004.

a) **Revised Sections Effective December 1, 2005**

- Section 7.1.3.

b) **New and Revised Sections Effective November 1, 2010**

- Section 2.1 – add “HRA” and Spot-Check definitions and revise the “Interchangeable” definition
- Section 2.2 – update the “Reference Publications”
- Section 10.2 – add “HRA”
- Section 14.1 and 14.2 – add “Spot-check” references

c) **Revised Sections to Meet the ALSC Glued Lumber Policy Effective November 9, 2015**

- Section 2.1
- Section 2.2 – update publication references
- Section 3.3.1, Section 9.2.1.6 and Section 10.2

d) **Revised Sections Effective May 1, 2026**

- Add changes to metric dimensions to align with PS 20 throughout the Standard
- Table 2 – update test values for S-P-F, D Fir-L (N), and North Species; revise Hem-Fir (N) test values based on approved new design values; and add 2x5 size
- Section 1.0 – edit and add Section 1.6
- Section 2.0 – add and update definitions and references
- Sections 3.3.1, new 7.1.4, and 10.2 – add “HRA” requirements
- Sections 3.0 to 11.0 – edit and clarify
- Section 9.3.2 – revise upper testing temperature for equipment and specimens
- Section 12 – update Quality Control Manual requirements
- Section 14 – update equipment calibration requirements
- Appendices – revise and update

## SPECIAL PRODUCTS STANDARD FOR STRUCTURAL FACE-GLUED LUMBER

### 1.0 SCOPE

#### 1.1 PART A AND PART B

This Standard consists of two parts.

##### PART A: PRODUCT SPECIFICATIONS

This Part specifies grade characteristics, standard sizes, visual grading and adhesive requirements, property requirements, property evaluation procedures, and grade stamping requirements for Structural Face-Glued lumber.

##### PART B: QUALIFICATION AND QUALITY CONTROL REQUIREMENTS

This Part specifies minimum qualifications and quality control requirements for a facility producing Structural Face-Glued lumber in accordance with the requirements of **Part A**.

#### 1.2 NLGA STANDARD GRADING RULES

This Standard shall be used in conjunction with and forms part of the National Lumber Grades Authority Standard Grading Rules for Canadian Lumber (NLGA Standard Grading Rules).

*Note: Paragraph numbers (NLGA Para. xx) referenced in this Standard refer to the numbered paragraphs in the NLGA Standard Grading Rules.*

#### 1.3 UNITS

This Standard states values in inch-pound (imperial) units. The equivalent SI (metric) values, given in parentheses, are provided for information only. In case of discrepancy, the values stated in imperial units shall take precedence.

#### 1.4 DESIGN VALUES

Structural face-glued lumber produced to the requirements of this Standard is assigned design values equivalent to visually graded non-face-glued solid-sawn lumber of the same grade, species group, and size.

For use in Canada, design values are assigned to visually graded lumber of equivalent grade by the CSA Group - Technical Committee on Engineering Design in Wood and are published in NLGA Para. 851 and in CSA O86.

For use in the U.S., design values are published in NLGA Paras. 902 and 904 and in the American Wood Council (AWC) National Design Specification (NDS) Supplement.

#### 1.5 STRUCTURAL FACE-GLUED LUMBER REQUIREMENTS

#### 1.5.1 GENERAL

This Standard applies to the manufacture and quality control of Structural Face-Glued lumber. The scope of products covered by this Standard shall meet the following criteria:

- a) Bonded surfaces between each lumber component shall run parallel to the edge,
- b) Bonded surfaces shall be flat with no profile included, and
- c) The final product shall have bonded surfaces that are only visible on the wide face of the full-size piece.

The quality of the components and the bonded surfaces shall be verified by inspection and test procedures. The quality of the full-size piece of face-glued lumber containing the bonded surfaces shall be verified by visual grading in accordance with NLGA Paras. 121 or 124.

#### 1.5.2 PERMITTED PRODUCT CONFIGURATIONS

The following product configurations are permitted under this Standard:

- a) Face gluing of solid sawn lumber components,
- b) Face gluing of solid sawn lumber components and ripping to nominal 2-inch thick lumber,
- c) Face gluing of fingerjoined lumber components meeting the requirements of NLGA SPS 1,
- d) Face gluing of fingerjoined lumber components meeting the requirements of NLGA SPS 1 and ripping to nominal 2-inch thick lumber.

*Note: See APPENDIX I for example products that fall within the scope of this Standard.*

#### 1.6 INTERPRETATIONS

The interpretations of the provisions in this Standard are vested in NLGA.

### 2.0 DEFINITIONS AND REFERENCED PUBLICATIONS

#### 2.1 DEFINITIONS

The following definitions shall apply to this Standard.

**AGENCY:** organization accredited by the Canadian Lumber Standards Accreditation Board (CLSAB) and/or the American Lumber Standard Committee (ALSC), Board of Review engaged in the grading, grade stamping and/or certification of lumber or who certifies facilities to grade and place a grade stamp upon lumber.

**AGENCY SUPERVISOR:** representative of the Agency who is approved by the Agency to inspect facilities producing structural face-glued lumber.

**AGENCY VERIFICATION:** specific set of procedures used by an Agency to verify that an item of grade stamped structural face-glued lumber conforms to the requirements of this Standard and the NLGA Standard Grading Rules.

**BONDED SURFACE:** location at which two components are held together with a layer of adhesive.

**BONDLINE:** layer of adhesive that attaches two components at the bonded surface.

**CALIBRATION:** procedure of comparing two instruments, measuring devices or standards, one of which is of known accuracy traceable to a nationally recognised standard.

**CHARACTERISTIC PROPERTY VALUE:** value corresponding to a percentile in the assumed statistical distribution of a particular property of the material.

*Note:* For the purpose of this Standard, characteristic strength values (i.e., MOR and Fv) are defined as the population 5th percentile values obtained under a short-term test load.

*Characteristic stiffness values (i.e., E<sub>5th</sub> and E) are defined as the population 5th percentile and mean value, respectively, obtained under a short-term test load.*

*The characteristic specific gravity is defined as the population mean value.*

**COMPONENTS:** lumber pieces that are used for the lay-up of structural face-glued lumber.

*Note:* Lumber components may also be referred to as candidate stock.

**CONFORMANCE:** state in which the production process meets the requirements of this Standard.

**CONTROL CHARTS:** reports or records used to monitor the variation between the process quality level and a predetermined conformance quality level, and to indicate when changes in the process are required to bring the process back into an “IN-CONTROL” state as defined by the conformance quality level.

**EVALUATION:** assessment of a facility’s manufacturing process and its quality control programs to determine whether it is capable of producing a product that meets the requirements of this Standard.

**FACE-GLUED LUMBER:** product made by bonding together two or more lumber components along longitudinal flat surfaces (without profiles) so that the grain of all laminations is essentially parallel and with bondlines located only on the wide face.

**FACILITY:** manufacturing plant that produces structural face-glued lumber and conducts visual grading and quality control sampling and testing.

**GRADE STAMP:** grade identification applied on a piece of structural face-glued lumber which includes the appropriate information specified under Section 10.2.

*Note:* The grade stamp (also referred to as a grade mark) indicates that the face-gluing process meets the requirements of the Agency’s qualification and quality control procedures.

**HEAT RESISTANT ADHESIVE (HRA):** designation on the grade stamp of structural face-glued lumber that indicates that the adhesive used in the bonding process meets the elevated temperature performance requirements of ASTM D7374 and CSA O177, Annex A.2.

**IN-CONTROL:** state in which on-going quality control testing indicates that the production process meets the mechanical property and delamination requirements of this Standard.

**INDEPENDENT CALIBRATION LABORATORY:** organization that performs testing to verify and establish results for test equipment, operating in accordance with ISO/IEC 17025 and accredited by an Accreditation Body listed under the ILAC Mutual Recognition Agreement (ILAC MRA).

**INSPECTION:** examination, measurement and/or testing of the properties of an item to ensure they meet the quality control requirements of this Standard.

**INTERCHANGEABLE:** capable of being assigned the design values of another product under certain end-use conditions.

*Note 1:* The specific end-use conditions for structural face-glued lumber are described in Section 3.1.

*Note 2:* Products are deemed to be interchangeable only to the extent established by the minimum requirements specified in this Standard. Comparability of properties not explicitly covered by this Standard may require additional assessment.

**ITEM:** lumber of a given grade, size (without reference to length), species or species group, and moisture content.

**NON-CONFORMANCE:** deficiency in a property, documentation or procedure that renders the quality of an item not to be in conformance to the requirements of this Standard and therefore unacceptable.

*Note:* Examples that may cause non-conformance include physical defects, test failures, incorrect or inadequate documentation, and deviations from prescribed processing, inspection or test procedures.

**OUT-OF-CONTROL:** state in which on-going quality control testing indicates that the production process does not meet the mechanical property and delamination requirements of this Standard.

**PRESSURE-VACUUM-DRY TREATMENT:** test procedure that provides an indication of the item’s ability to resist exposure conditions normally encountered during shipment, storage, and/or use.

**QUALITY CONTROL:** set of procedures that provide a means of measuring and regulating the performance of an item to specified requirements.

**QUALITY CONTROL MANUAL:** document which sets forth a specific set of instructions to describe the quality control functions and requirements to be carried out in the production of structural face-glued lumber at a specified facility.

*Note:* Also referred to as a Plant Standard.

**RANDOM SAMPLING:** a procedure by which a representative sample is generated from a population.

**RE-QUALIFICATION:** analysis of the test results from a random sample drawn from a process that has undergone corrective action in response to an “**OUT-OF-CONTROL**” condition or re-establishing conformance of items where production has ceased for a period exceeding one year.

**SEPARATE-APPLICATION ADHESIVE:** multi-component adhesive that has the following characteristics:

- a) Each adhesive component is applied separately to one or both sides of the bonded surface along the bondline.
- b) All adhesive components are required for the bond strength to be fully developed.
- c) Some separate-application adhesives require that the components be **blended** for the adhesive to develop the required strength and durability. Other systems simply require the components to contact each other.

*Note:* “Blended” is defined as thoroughly mixing the adhesive components together resulting in a homogeneous mixture.

**SHIPMENT:** one or more bundles, packages or units of lumber that comprise an order.

**SPECIMEN:** piece of full-size structural face-glued lumber randomly selected from production for purposes of quality control, quality verification testing and any subsequent analysis.

**SPOT CHECK:** verification that the test equipment is still within calibration tolerances.

**SUBSEQUENT QUALIFICATION:** analysis of the test results from a random sample drawn from a process whose production is in-conformance with the requirements of this Standard but has been modified for reasons other than to respond to a detection of non-conformance.

*Note:* Subsequent Qualification procedures apply only to the process changes specified in this Standard. Other process changes are evaluated using the Initial Qualification procedures.

**TEST BLOCK:** piece of structural face-glued lumber cut from a full-size specimen selected for purposes of quality verification testing and any subsequent analysis.

**TEST EQUIPMENT:** equipment used by the facility to determine the bending and shear strength properties of a specimen for the purpose of determining conformance to the specified requirements of this Standard.

**TEST LOAD:** load that will induce a stress that corresponds to the characteristic property value for the item under consideration.

**WOOD FAILURE:** failure induced at the bondline where the bonded surface fails by the tearing of wood fibre from one or both side(s) of the bondline.

2.2

**REFERENCED PUBLICATIONS**

AITC (American Institute of Timber Construction)

**Test Methods for Structural Glued Laminated Timber:** AITC Test T107 – Shear Test (2007)

ALSC (American Lumber Standard Committee, Inc.)

**Glued Lumber Policy** (2024)

AWC (American Wood Council)

**National Design Specification (NDS®) Supplement:** Design Values for Wood Construction (2024)

ASTM International

**D905-08 (2021)** Standard Test Method for Strength Properties of Adhesive Bonds in Shear by Compression Loading

**D1101-97a (2024)** Standard Test Methods for Integrity of Glue Joints in Structural Laminated Wood Products for Exterior Use

**D1990-24** Standard Practice for Establishing Allowable Properties for Visually-Graded Dimension Lumber from In-Grade Tests of Full-Size Specimens

**D4444-13 (2018)** Standard Test Methods for Laboratory Standardization and Calibration of Hand-Held Moisture Meters

**D5266-13 (2020)** Standard Practice for Estimating the Percentage of Wood Failure in Adhesive Bonded Joints

**D7374-21** Standard Practice for Evaluating Elevated Temperature Performance of Adhesives Used in End-Jointed Lumber

**D7438-20** Standard Practice for Field Calibration and Application of Hand-Held Moisture Meters

**E4-24** Standard Practices for Force Calibration and Verification of Testing Machines

**E74-18e1** Standard Practices for Calibration and Verification for Force-Measuring Instruments

**CLSAB** (Canadian Lumber Standards Accreditation Board)

**Regulations** (2024)

**CSA Group**

**CSA O86:24** Engineering design in wood

**CSA-O112.7:M1977 (R2006)** Resorcinol and phenol-resorcinol resin adhesives for wood

**CSA-0112.9:21** Evaluation of adhesives for structural wood products (exterior exposure)

**CSA O141:23** Canadian standard lumber

**CSA O122:24** Structural glued-laminated timber

**CSA O177:23** Qualification code for manufactures

of structural glue-laminated lumber

**ISO** (International Organization for Standardization)

**ISO/IEC 17025: 2017 (c2023)** General Requirements for the Competence of Testing and Calibration Laboratories

**ISO/IEC 17065: 2012 (c2024)** Conformity Assessment – Requirements for Bodies Certifying Products, Processes and Services

**NIST** (National Institute of Standards and Technology, U.S. Department of Commerce)

**PS 20-25** American Softwood Lumber Standard

**NLGA** (National Lumber Grades Authority)

**Standard Grading Rules for Canadian Lumber** (2022)

**SPS 1** Special Products Standard for Fingerjoined Structural Lumber (2023)

## PART A - PRODUCT SPECIFICATIONS FOR STRUCTURAL FACE-GLUED LUMBER

### 3.0 PRODUCT DESCRIPTION

#### 3.1 APPLICATIONS AND INTERCHANGEABILITY

Structural face-glued lumber produced to the requirements of this Standard is interchangeable with visually graded non-face-glued lumber of the same grade, size, and species or species group subject to the following restrictions:

- a) Structural face-glued lumber shall not be visually re-graded or re-manufactured into a higher stress grade even if the quality of the lumber containing bonded surfaces could otherwise warrant such re-grading,
- b) Face-gluing of chemically treated lumber or chemical treatment of structural face-glued lumber are not within the scope of this Standard.

**Note:** *This product is intended for use as a joist, rafter or stud member in a repetitive member assembly, or headers, lintels or built-up beams. Its suitability for use as a component in other products and applications should be assessed in accordance with the applicable product standard.*

### 3.2 DEMONSTRATION OF CONFORMANCE

Structural face-glued lumber represented as conforming to the requirements of this Standard shall be manufactured using a process in which the quality of the bonded surface produced is continuously monitored in accordance with all the requirements specified herein. Product conformance information shall be maintained through records and charts recording the results of the inspection and test procedures.

### 3.3 SPECIAL APPLICATIONS

#### 3.3.1 HEAT RESISTANT ADHESIVES

Structural face-glued lumber is manufactured with a heat-resistant adhesive that meets the requirements of Section 7.1.4.

#### 3.3.2 RE-WORKING OF STRUCTURAL FACE-GLUED LUMBER

Modifications or additional manufacturing activities on structural face-glued lumber are outside the scope of this Standard.

*Note: Examples of modifications or further activities are alterations to the lumber cross-section such as drilling of holes or profiling.*

**4.0 GRADE DESCRIPTION**

This Standard applies to structural face-glued lumber visually graded to the NLGA grades shown in Table 2, based on the grade descriptions in NLGA Paras. 121 and 124 for the species and species groups as specified in Section 6.1.

**5.0 STANDARD SIZES**

Structural face-glued lumber produced in accordance with this Standard shall be manufactured in nominal sizes 2x3 through 2x12 and in lengths not to exceed 24 feet (7.32 m).

Standard thicknesses and widths are shown in Table 1.

**TABLE 1 - STANDARD THICKNESSES AND WIDTHS (AS SPECIFIED IN CSA O141 AND PS 20)**

Nominal Dimension	Specified Surfaced Dimension			
	inches		mm	
	Dry	Green	Dry	Green
<b>Thickness</b>				
<b>2</b>	1-1/2	1-9/16	38.1	39.7
<b>Width</b>				
<b>2</b>	1-1/2	1-9/16	38.1	39.7
<b>3</b>	2-1/2	2-9/16	63.5	65.1
<b>4</b>	3-1/2	3-9/16	88.9	90.5
<b>5</b>	4-1/2	4-5/8	114.3	117.5
<b>6</b>	5-1/2	5-5/8	139.7	142.9
<b>8</b>	7-1/4	7-1/2	184.2	190.5
<b>10</b>	9-1/4	9-1/2	235.0	241.3
<b>12</b>	11-1/4	11-1/2	285.8	292.1

**6.0 LUMBER COMPONENT REQUIREMENTS**

**6.1 SPECIES**

The lumber components used in the manufacture of structural face-glued lumber may be of any species in the species groups specified in NLGA Paras. 7 and 7a.

Individual species of a species group shall be combined in any combination that preserves the species group. Components from different species groups shall not be mixed within the same production item.

**6.2 LUMBER COMPONENTS**

**6.2.1 COMPONENT SIZE**

Structural face-glued lumber shall be formed from lumber components that are not less than 1/2 inch (12.7 mm) surfaced size in thickness.

**6.2.2 FINGERJOINED COMPONENTS**

When fingerjoined lumber components are used in the assembly of structural face-glued lumber under this Standard, the following shall apply:

**6.2.2.1 COMPONENT REQUIREMENTS**

The fingerjoined lumber components shall have met the strength and delamination requirements of NLGA SPS 1 for each size and grade used. The grade of the lumber components shall meet or exceed the highest structural face-glued lumber grade to be produced in the facility.

**6.2.2.2 FINGERJOINT QUALIFICATION AND QUALITY CONTROL REQUIREMENT**

The facility layout, production sequence and identification of the fingerjoined lumber components shall be described in the Quality Control Manual. The facility shall ensure that all lumber components in the final product originate and can be verified to have originated from fingerjoined production that meets the NLGA SPS 1 requirements for the grade(s) being produced.

**6.2.3 COMPONENT WOOD QUALITY**

Structural face-glued lumber shall be formed with lumber components that meet or exceed the visual grading requirements of the grade of structural face-glued lumber being produced, with the following exceptions:

- a) **Knots or Holes:** shall not occupy more than 3/4 of the cross-section in each component.

*Note: Although this component knot size is larger than the allowable knot in the lowest visual grade of NO. 3 / STUD, the finished structural face-glued product must still meet the visual grading requirements for the final product grade being grade stamped.*

- b) **Wane:** shall not exceed 1/3 the thickness and 1/3 of the width.

*Note: Wherever possible, wane on the two components forming the face-glued lumber should not be placed along the same section of bondline.*

- c) **Compression wood:** severe compression wood is not permitted.

- d) **Honeycomb and Decay:** not permitted in the bonded surface area.

- e) **Pitch:** shall not exceed half the thickness and half the width.

**6.2.4 MOISTURE CONTENT**

Green and dry lumber components shall not be mixed within the same piece.

**6.3 FINISHED PRODUCT LUMBER QUALITY**

**6.3.1 VISUAL GRADE**

The finished structural face-glued product shall be visually graded in accordance with the provisions of the NLGA Standard Grading Rules for the grade being grade-stamped except as provided in Sections 6.3.2 and 6.3.3.

**6.3.2 WHITE SPECKS (NO. 2, NO. 3, AND STUD GRADES)**

White specks are unlimited if only occurring on one side of the bond line. White specks occurring along both sides of the bond line are not permitted to overlap in the same cross-section.

**6.3.3 OFFSET (STUD GRADE ONLY)**

Offset between bonded surfaces of STUD grade structural face-glued lumber shall not exceed 1/16 inch (1.6 mm) on occasional pieces.

**7.0 ADHESIVE REQUIREMENTS**

**7.1 ADHESIVE SPECIFICATION**

**7.1.1 GENERAL**

The adhesive used for face gluing shall meet Section 7.1.4 and either Section 7.1.2 or Section 7.1.3 of this Standard.

**7.1.2 RESORCINOL AND PHENOL RESORCINOL ADHESIVES**

The adhesive used for face gluing shall meet the requirements of CSA O112.7.

*Note: The adhesive may be mixed with the minimum amount of inert fillers required for its performance in the particular process being used.*

**7.1.3 ALTERNATE ADHESIVES**

The adhesive used for face gluing shall meet the requirements of CSA O112.9 when evaluated for one of the softwood species specified in that Standard.

**7.1.4 ELEVATED TEMPERATURE ADHESIVES**

The heat resistant adhesive (HRA) used for face gluing shall meet the requirements of ASTM D7374 and CSA O177, Annex A.2.

If fingerjoined lumber components were utilized in the manufacture of the structural face-glued product, the adhesive used in fingerjoining shall have met the requirements of ASTM D7374 as per NLGA SPS 1.

**7.2 SEPARATE APPLICATION ADHESIVES**

Separate application adhesives are not permitted.

**7.3 ADHESIVE MIXING**

Mixing of the adhesive shall be performed in accordance with the instructions provided by the adhesive supplier.

**7.4 BONDED SURFACE FABRICATION**

**7.4.1 ADHESIVE APPLICATION**

The adhesive shall be applied in a manner that ensures that all gluing surface between the faces receives enough adhesive resulting in squeeze out of excess adhesive when assembling pressure is applied.

*Note: The adhesive may be applied to one or both faces forming the bonded surface.*

**7.4.2 HEAT DAMAGE**

Where a procedure is used to apply heat to the bonded surface, it shall be such as to ensure that neither the wood faces in the bonded surface nor the surrounding wood are damaged by excess heat.

*Note: In Radio Frequency (RF) curing, wood damage may result from excessively long exposure of the bonded surface to the RF field. In either situation both the strength and the long-term durability of the bonded surface may be impaired.*

**7.4.3 ASSEMBLY PRESSURE**

The pressure applied during the bonded surface assembly process, and while the bondline is being cured, shall be that required for the lumber size, species, and gluing process used.

Pressure shall be applied uniformly over the entire bonding surface.

**8.0 PROPERTY REQUIREMENTS FOR STRUCTURAL FACE-GLUED LUMBER**

The following property requirements for structural face-glued lumber are based on the test values listed in Table 2.

**8.1 MODULUS OF RUPTURE (MOR)**

The process lower fifth percentile for edge-wise bending modulus of rupture ( $MOR_{5th}$ ) shall equal or exceed the MOR test value for the size, grade, and species group as provided in Table 2 when subjected to a short-term test load and tested in accordance with Section 9.1.

$$MOR_{5th} \geq MOR$$

## 8.2 SHEAR STRENGTH PARALLEL TO GRAIN ( $F_v$ )

The process lower fifth percentile for shear strength parallel to grain ( $F_{v5th}$ ) shall equal or exceed the shear strength parallel to grain ( $F_v$ ) test value for the species group as provided in Table 2 when subjected to a short-term test load and tested in accordance with Section 9.2.

$$F_{v5th} \geq F_v$$

## 8.3 WOOD FAILURE

### 8.3.1 GENERAL

Wood failure shall be assessed in accordance with Section 9.2.4. Any separation of the bondline in the final product shall be investigated. If necessary, additional physical testing shall be undertaken.

*Note: See APPENDIX VI for commentary on wood failure assessment.*

### 8.3.2 AVERAGE WOOD FAILURE

The “Average” wood failure of the test results shall equal or exceed 80% wood failure.

### 8.3.3 MINIMUM WOOD FAILURE

“All” of the wood failure test results shall equal or exceed 60% wood failure.

## 8.4 FINAL GRADE

The final grade of structural face-glued lumber shall be determined by the lower of the visual grade of the lumber or the stress grade determined by strength tests on the bonded surfaces.

TABLE 2 – PROPERTY TEST VALUES FOR STRUCTURAL FACE-GLUED LUMBER

Nominal Size	Grade	MOR [Bending Strength] (psi)	Fv [Shear Strength Parallel to Grain] (psi)
<b>S-P-F</b>			
<b>2x3</b>	Sel Str	3940	<b>285</b>
	No. 1 / No. 2	2790	
	No. 3 / Stud	1650	
<b>2x4</b>	Sel Str	3940	
	No. 1 / No. 2	2790	
	No. 3 / Stud	1650	
<b>2x5</b>	Sel Str	3680	
	No. 1 / No. 2	2570	
	No. 3 / Stud	1470	
<b>2x6</b>	Sel Str	3410	
	No. 1 / No. 2	2390	
	No. 3 / Stud	1370	
<b>2x8</b>	Sel Str	3150	
	No. 1 / No. 2	2210	
	No. 3 / Stud	1260	
<b>2x10</b>	Sel Str	2890	
	No. 1 / No. 2	2020	
	No. 3 / Stud	1160	
<b>2x12</b>	Sel Str	2630	
	No. 1 / No. 2	1840	
	No. 3 / Stud	1050	
<b>Hem-Fir (N)</b>			
<b>2x3</b>	Sel Str	3800	<b>305</b>
	No. 1 / No. 2	3150	
	No. 3 / Stud	1810	
<b>2x4</b>	Sel Str	3800	
	No. 1 / No. 2	3150	
	No. 3 / Stud	1810	
<b>2x5</b>	Sel Str	3530	
	No. 1 / No. 2	2940	
	No. 3 / Stud	1690	
<b>2x6</b>	Sel Str	3280	
	No. 1 / No. 2	2730	
	No. 3 / Stud	1570	
<b>2x8</b>	Sel Str	3020	
	No. 1 / No. 2	2520	
	No. 3 / Stud	1450	
<b>2x10</b>	Sel Str	2770	
	No. 1 / No. 2	2310	
	No. 3 / Stud	1330	
<b>2x12</b>	Sel Str	2520	
	No. 1 / No. 2	2100	
	No. 3 / Stud	1210	
<b>D Fir-L (N)</b>			
<b>2x3</b>	Sel Str	4160	<b>380</b>
	No. 1 / No. 2	2680	
	No. 3 / Stud	1510	
<b>2x4</b>	Sel Str	4160	
	No. 1 / No. 2	2680	
	No. 3 / Stud	1510	
<b>2x5</b>	Sel Str	3880	
	No. 1 / No. 2	2500	
	No. 3 / Stud	1410	
<b>2x6</b>	Sel Str	3600	
	No. 1 / No. 2	2320	
	No. 3 / Stud	1310	
<b>2x8</b>	Sel Str	3330	
	No. 1 / No. 2	2140	
	No. 3 / Stud	1210	
<b>2x10</b>	Sel Str	3050	
	No. 1 / No. 2	1960	
	No. 3 / Stud	1110	
<b>2x12</b>	Sel Str	2770	
	No. 1 / No. 2	1790	
	No. 3 / Stud	1010	
<b>Northern Species</b>			
<b>2x3</b>	Sel Str	3150	<b>230</b>
	No. 1 / No. 2	1890	
	No. 3 / Stud	1100	
<b>2x4</b>	Sel Str	3150	
	No. 1 / No. 2	1890	
	No. 3 / Stud	1100	
<b>2x5</b>	Sel Str	2940	
	No. 1 / No. 2	1760	
	No. 3 / Stud	1030	
<b>2x6</b>	Sel Str	2730	
	No. 1 / No. 2	1640	
	No. 3 / Stud	960	
<b>2x8</b>	Sel Str	2520	
	No. 1 / No. 2	1510	
	No. 3 / Stud	880	
<b>2x10</b>	Sel Str	2310	
	No. 1 / No. 2	1390	
	No. 3 / Stud	810	
<b>2x12</b>	Sel Str	2100	
	No. 1 / No. 2	1260	
	No. 3 / Stud	740	
<p><b>Note:</b> Derived from the design values of the AWC - NDS Supplement or CSA O86 - Engineering design in wood, whichever is a higher property value for a given size / grade / species group.</p>			

**9.0 STRUCTURAL FACE-GLUED LUMBER PROPERTY EVALUATION PROCEDURES**

**9.1 MODULUS OF RUPTURE (MOR)**

MOR shall be determined by applying a test load to a full-size specimen that will induce a maximum stress not less than the MOR test value for the grade, size, and species group under consideration (see Table 2).

Specimens shall be tested on edge using third point loading and a span to depth ratio of 21 whenever possible. The specimen depth is the surfaced dry width as provided in Table 1. If a span to depth ratio of 21 cannot be achieved the span shall be the maximum span possible and the MOR test value in Table 2 shall be adjusted for a shorter span using the correction factors or equation found in APPENDIX II.

The maximum strength-reducing characteristic as determined by visual grading shall be located in the middle third of the test span, or as close to the middle third as possible.

For test equipment where the load is applied vertically and where there is more than 5 inches (127 mm) of length overhanging beyond either of the reaction supports, the calculated MOR shall be corrected for the weight of the overhanging portions.

Corrections are not required provided it can be demonstrated that neglecting the correction ensures a lower MOR value or where specimens are tested with the load applied in a horizontal direction.

**9.2 SHEAR STRENGTH PARALLEL TO GRAIN (F<sub>v</sub>)**

**9.2.1 TEST BLOCK PREPARATION**

Shear block test specimens shall be randomly selected from normal production.

One block shall be sawn from each specimen in clear wood with no apparent strength-reducing characteristics. Care shall be taken in preparing the test blocks to make loaded surfaces smooth and parallel to each other and perpendicular to height.

The test blocks shall be prepared in accordance with AITC Test T107 as illustrated in APPENDIX III.

After test block preparation, test blocks shall be subjected to the pressure-vacuum-dry treatment as specified in APPENDIX IV.

The shear area dimensions shall be measured to the nearest 0.004 inch (0.10 mm) at the bondline after the pressure-vacuum-dry treatment and prior to testing.

**9.2.2 SHEAR STRENGTH PARALLEL TO GRAIN TEST PROCEDURE**

Each test block shall be tested in accordance with ASTM D905.

Crosshead movement shall provide approximately a uniform rate of loading not to exceed 0.50 inch (12.7 mm) per minute.

**9.2.3 MULTIPLE BONDED SURFACE TEST BLOCKS**

For test blocks having multiple bonded surfaces, repeat the test procedure specified in Section 9.2.2 to evaluate every bonded surface present in the test block. Report the shear strength value and the wood failure from the bondline with the lowest shear strength value from each test block with multiple bonded surfaces.

**9.2.4 WOOD FAILURE READING PROCEDURE**

Trained personnel shall read wood failure.

*Note: ASTM D5266 has been found useful in estimating the percentage of wood failure in adhesive bonded surfaces.*

**9.2.5 CALCULATION AND REPORT**

Shear strength shall be calculated from the recorded failing load and the measured shear area. The percentage of wood failure shall be determined on this area.

The specimen shear strength value shall be taken from the lowest test block value.

*Note 1: A maximum of one specimen may be rejected if a grade defect is detected after the shear block test and the test block shear strength is below the minimum required shear strength.*

*Note 2: The Agency may request a facility to hold the test blocks intact for examination by the Agency supervisor.*

**9.3 ENVIRONMENTAL CONDITIONS**

**9.3.1 MEASUREMENT OF MOISTURE CONTENT AT TIME OF TEST**

For each test block, a moisture content measurement using a resistance type moisture meter shall be made on each side of the bondline and sufficiently away from the bonding surface so that the meter readings are not influenced by the presence of the adhesive. Each of the readings shall be recorded as the moisture content of the specimen's component(s) at the time of test.

**9.3.2 TEMPERATURE**

**9.3.2.1 TEST EQUIPMENT**

The temperature of the test equipment shall, at the time of the test, be in the range of 50 to 95° F (10 to 35° C) inclusive. If the test equipment is operated at temperatures below 50° F (10° C), the equipment shall be calibrated at a temperature within ±10° F (5° C) of the temperature at which the equipment will be operated.

**9.3.2.2 TEST SPECIMENS**

Test specimens shall be stored under the same environmental conditions (within ±10° F (5° C)) as the production run until the start of the structural face-glued lumber property evaluation procedures.

## 10.0 GRADE STAMPING OF STRUCTURAL FACE-GLUED LUMBER

### 10.1 GENERAL

A grade stamp on structural face-glued lumber indicates that the grading process meets the requirements of the Agency's qualification and quality control procedures.

All previous grade stamps on lumber components shall be removed or obliterated.

## 10.2 GRADE STAMP REQUIREMENTS

Grade stamps on structural face-glued lumber produced in conformance with the requirements of this Standard and the NLGA Standard Grading Rules shall provide the following information:

- a) Visual grade assigned to the piece,
- b) Species or species group identification,
- c) Seasoning designation,
- d) Registered symbol of the Agency,
- e) Facility identification,
- f) Designation of "SPS 6" and "CERT FACE-GLUED LBR",
- g) Designation of "NLGA" to indicate the grading rules used, and
- h) Designation of "HRA".

## PART B - QUALIFICATION AND QUALITY CONTROL REQUIREMENTS

### 11.0 EQUIPMENT

The facility's test equipment shall meet the following requirements:

#### 11.1 MOR TEST EQUIPMENT

The bending test equipment shall provide for roller action on the reaction supports and sufficient radius on the loading points to avoid significant crushing of wood. Side supports to prevent the buckling of lumber shall also be provided.

The test span and location of the load points shall be capable of being set to within  $\pm 1/16$  inch (1.6 mm).

The load-measuring device shall be accurate to within  $\pm 2\%$  of the actual load.

The load shall be applied through a crosshead. The rate of the crosshead movement shall not exceed 5 inches/minute (2.1 mm/second) during specimen testing.

#### 11.2 SHEAR PARALLEL TO GRAIN TEST EQUIPMENT

The block shear test equipment shall be capable of performing shear strength tests in accordance with ASTM D905.

The load-measuring device shall be accurate to within  $\pm 2\%$  of the actual load.

The rate of loading shall be within 0.015 to 0.5 inches (0.38 to 12.7 mm) per minute.

#### 11.3 PRESSURE-VACUUM-DRY TREATMENT EQUIPMENT

#### 11.3.1 PRESSURE VESSEL

An autoclave or similar pressure vessel designed to safely withstand and maintain a pressure of at least 100 psi (0.7 MPa) is required for impregnating the specimens with water. The pressure vessel shall be equipped with a means of obtaining a vacuum of at least 25 inches (635 mm) of mercury (at sea level) and a means of obtaining a pressure of at least 75 psi (0.52 MPa). The vessel shall be equipped with a gauge(s) to register vacuum and pressure.

**Note:** A suitable vacuum may be obtained from an aspirator attached to the water supply, and 75 psi (0.52 MPa) can usually be obtained from a municipal water supply or a compressed air supply.

#### 11.3.2 DRYING OVEN

The drying oven shall be capable of maintaining the conditions necessary to dry specimens to a moisture content of 19% or less.

**Note:** These drying conditions are obtainable in cross-flow, laboratory type ovens of the circulating type. They can also be obtained by using a non-circulating configuration in which air heated by a space heater is passed over the specimens and vented.

Conditions that affect the drying rate include cross-flow air velocity, humidity, air temperature and the arrangement, size and number of specimens in the oven.

Circulating type ovens that provide a cross-flow air velocity of 250 fpm (75 m/min) in the centre of the drying chamber and maintain an air temperature of 160° F (71° C) should be capable of achieving the specified drying rate.

**12.0 QUALITY CONTROL MANUAL**

**12.1 GENERAL**

The Quality Control (QC) Manual is a document outlining the requirements for maintaining quality control in the manufacturing facility.

*Note: See APPENDIX V for a general commentary on the contents of a QC Manual.*

All production quality control procedures shall comply with the requirements of this Standard and the QC Manual.

**12.2 PREPARATION, REVISION AND APPROVAL**

Each facility shall:

- a) Prepare a QC Manual in compliance with this Standard and submit the manual to the Agency for approval,
- b) Regularly review and update its QC Manual to reflect current production practices and procedures, quality control policies and quality control program procedures and resubmit to the Agency for approval, and
- c) Upon approval, implement the new or updated procedures in accordance with the QC Manual.

The Agency shall approve the contents of the QC Manual at the time of qualification. Qualification shall apply only to the manufacturing, quality control procedures and limits set forth in the QC Manual.

The Agency shall be notified in advance of any changes in the QC Manual that may affect product quality.

**12.3 CONTENTS**

**12.3.1 AGENCY**

The QC Manual shall identify the CLSAB and/or ALSC accredited Agency and include a summary of the following:

- a) That the Agency certification and quality control procedures for structural face-glued lumber comply with the CLSAB Regulations and ALSC Glued Lumber Policy,
- b) That the responsibility for the certification and quality control procedures is that of the Agency, and
- c) That the CLSAB and the ALSC shall monitor whether the certification and quality control procedures are being carried out by the Agency.

**12.3.2 GENERAL FACILITY ADMINISTRATION**

The QC Manual shall:

- a) Define facility management policies, objectives, and responsibilities for quality control, including the responsibility for each division within a multi-division organization,

- b) Define the responsibility and authority for those managing and performing the quality control work and of those that are confirming conformance to quality control requirements,

*Note: Facility management relationships may be shown on organization charts.*

- c) Identify the Supervisor who shall report directly to management at a level to ensure that quality control requirements are not subordinated to manufacturing or sales. The QC Manual shall define the Supervisor's authority to resolve quality control matters, and
- d) Define the responsibility and authority of personnel responsible for quality control and their organizational freedom to:
  - i) Identify and record non-conformance to quality,
  - ii) Recommend or provide solutions through designated positions in the organization,
  - iii) Confirm implementation of solutions, and
  - iv) Oversee further processing of a non-conforming item(s) until the deficiency or unsatisfactory condition has been corrected.

**12.3.3 FACILITY QUALITY CONTROL PERSONNEL**

The QC Manual shall outline the responsibilities of the quality control personnel.

Persons responsible for quality control shall possess and demonstrate to the satisfaction of the Agency that they have adequate knowledge of the manufacturing process, which shall include:

- a) Inspection and test procedures used to control the process,
- b) Operation and calibration of the recording and test equipment used, and
- c) Maintenance and interpretation of quality control records.

In addition, the quality control personnel shall be responsible for carrying out and maintaining records of various inspections and test procedures detailed in the QC Manual.

The quality control personnel shall also formally advise the facility management of circumstances resulting from the inspections and test procedures that indicate corrective action may be necessary in the production process.

**12.3.4 FACILITY QUALITY CONTROL PROCEDURES**

The QC Manual shall include detailed procedures specifying how each of the following is to be performed and controlled:

- a) Lay-up machine operation,

- b) Test equipment operation including calibration and spot-check procedures.
- c) Quality control sampling, testing and analysis,
- d) Documentation and record keeping,
- e) Identification and traceability,
- f) Non-conformance, and
- g) Corrective action.

**13.0 QUALIFICATION REQUIREMENTS**

**13.1 INITIAL FACILITY QUALIFICATION**

A facility requesting initial qualification shall provide the Agency with evidence that all the requirements of **Part A** have been met. Upon receipt of the request, the Agency supervisor shall visit the facility to determine that:

- a) The facility is capable of operating within the requirements of this Standard and its QC Manual,
- b) The facility personnel possess ability to undertake the requirements described in Section 12, and
- c) The calibration of the test equipment conforms to the requirements of the QC Manual.

The facility shall generate samples prior to initial qualification sampling as per Section 13.2. The Agency supervisor shall sample for initial qualification as per Section 13.3.

Each item shall be qualified before issuing grade stamps.

**13.2 NEW PRODUCTION LINE START-UP OR MAJOR CHANGE REQUIREMENTS (To be Performed by the Facility)**

During start-up of a new production line or when a major change to the structural face-glued lumber process occurs, the facility shall immediately notify the Agency.

**13.2.1 NEW PRODUCTION LINE START-UP OR CHANGES REDUCING JOINT SPACING (When Fingerjoined lumber components are used to produce Structural Face-Glued Lumber)**

Prior to the initial qualification testing, the facility under the supervision of the Agency shall generate or select a **28**-specimen sample that meets the following characteristics:

- a) The average fingerjoint spacing shall be equal to or less than the fingerjoint spacing to be used, and
- b) At least one section between the load points includes fingerjoints in adjacent laminations that are aligned in the cross-section. The fingerjoints are considered to be aligned if the tips of adjacent fingerjoints overlap.

The specimens shall be tested in accordance with Section 13.2.3.

**13.2.2 NEW PRODUCTION LINE START-UP OR OTHER MAJOR CHANGES (To be Performed by the Facility)**

Prior to grade stamps being issued for lumber from the new production line or to continue grade-stamping privileges in the case of a major change(s), the facility shall provide the Agency with test results of **53** bending strength, **53** shear strength parallel to grain, and **53** wood failure assessments.

The specimens for these tests shall be obtained from a single item, consisting of the densest species or species group and using a procedure, approved by the Agency, which ensures the samples obtained are representative of the item to be qualified.

The specimens shall be tested in accordance with Section 13.2.3.

**13.2.3 PLANT QUALIFICATION TEST PROCEDURE**

The specimens shall be tested in accordance with Section 9 and the test results shall meet the requirements set forth in Section 13.5.1.

*Note: The bending strength, shear strength parallel to grain and wood failure tests are required in the initial start-up of a face-gluing line or when there is a major change to the gluing process: They are intended to verify the adequacy of the bonding surface and do not substitute for the test qualification requirements called for in Section 13.3 of this Standard.*

Grade stamping shall be contingent upon verification of the item in accordance with Section 13.3 of this Standard.

**13.3 INITIAL QUALIFICATION SAMPLING (To be Performed by the Agency)**

The Agency supervisor shall randomly select the following samples for each item to be qualified:

**13.3.1 BENDING STRENGTH**

A **53**-specimen sample of structural face-glued lumber for bending strength (MOR) evaluations to be tested in accordance with Section 9.1 of this Standard.

*Note: Additional specimens to increase the sample size to 78, 102, 125, or 148 may be selected to qualify the bending strength.*

**13.3.2 SHEAR STRENGTH AND WOOD FAILURE ASSESSMENT**

A **53**-specimen sample of structural face-glued lumber for shear strength parallel to grain (Fv) evaluations to be tested in accordance with Section 9.2 of this Standard and assessed for percentage wood failure in accordance with Section 9.2.4 of this Standard.

*Note: Additional specimens to increase the sample size to 78, 102, 125, or 148 may be selected to qualify the shear strength and/or wood failure.*

**13.4 RE-QUALIFICATION SAMPLING**

For items that are deemed to be “OUT-OF-CONTROL”, the facility shall randomly select specimens from production for re-qualification. The minimum sample size for each item and for each property to be re-qualified is as follows:

**13.4.1 BENDING STRENGTH**

When the bending strength is required to be re-qualified, **28** specimens for the bending strength (MOR) evaluations shall be selected. The specimens shall be tested in accordance with Section 9.1.

*Note: Additional specimens to increase the sample size to **53, 78, 102, 125, or 148** may be selected to re-qualify the bending strength.*

**13.4.2 SHEAR STRENGTH AND WOOD FAILURE ASSESSMENT**

- a) When the shear strength parallel to grain is required to be re-qualified, **28** specimens for the shear strength parallel to grain (Fv) evaluations shall be selected. The specimens shall be tested in accordance with Section 9.2.
- b) When wood failure is required to be re-qualified, wood failure assessment shall be performed from the **28** specimens selected in Section 13.4.2a).

*Note: For items a) and b) above, additional samples to increase the sample size to **53, 78, 102, 125, or 148** may be selected to re-qualify the shear strength and/or wood failure.*

**13.5 DECISION RULES**

**13.5.1 INITIAL QUALIFICATION RULES**

Results of bending strength tests, shear strength tests and wood failure assessments shall determine whether grade stamps will be issued for the item being qualified.

An item shall be considered qualified when all the following requirements are met:

**13.5.1.1 BENDING STRENGTH (MOR)**

Not more than **1** of the **53** bending strength test results shall have a MOR value less than the MOR test value for the size, grade, and species group as provided in Table 2.

When the additional specimen sampling procedure referred to in Section 13.3 is used to qualify for bending strength, not more than **2** test results in a **78**; **3** in a **102**; **4** in a **125**; or **5** in a **148**-specimen sample shall have a bending strength value less than the corresponding MOR test value for the size, grade, and species group as provided in Table 2.

**13.5.1.2 SHEAR STRENGTH PARALLEL TO GRAIN (Fv)**

Not more than **1** of the **53** shear strength test results shall have a shear strength value less than the Fv test value for the species group as provided in Table 2.

When the additional specimen sampling procedure referred to in Section 13.3 is used to qualify for shear strength parallel to grain, not more than **2** test results in a **78**; **3** in a **102**; **4** in a **125**; or **5** in a **148**-specimen sample shall have a shear strength value less than the corresponding Fv test value for the species group as provided in Table 2.

**13.5.1.3 WOOD FAILURE**

The “Average” wood failure test results for the specimens shall equal or exceed 80% wood failure.

“All” the specimen wood failure test results shall equal or exceed 60% wood failure.

**13.5.2 RE-QUALIFICATION RULES**

An item shall be considered re-qualified when all the following requirements are met:

**13.5.2.1 BENDING STRENGTH (MOR)**

“All” the **28** bending strength test results shall equal or exceed the MOR test value for the for the size, grade, and species group as provided in Table 2.

When the additional specimen sampling procedure referred to in Section 13.4 is used to re-qualify for bending strength, not more than **1** test result in a **53**; **2** in a **78**; **3** in a **102**; **4** in a **125**; or **5** in a **148**-specimen sample shall have a bending strength value less than the corresponding MOR test value for the size, grade, and species group as provided in Table 2.

**13.5.2.2 SHEAR STRENGTH PARALLEL TO GRAIN (Fv)**

“All” of the **28** shear strength test results shall equal or exceed the Fv test value for the species group as provided in Table 2.

When the additional specimen sampling procedure referred to in Section 13.4 is used to re-qualify for shear strength, not more than **1** test result in a **53**; **2** in a **78**; **3** in a **102**; **4** in a **125**; or **5** in a **148**-specimen sample shall have a shear strength value less than the corresponding Fv test value for the species group as provided in Table 2.

**13.5.2.3 WOOD FAILURE**

The “Average” wood failure test results for the specimens shall equal or exceed 80% wood failure.

“All” of the specimen wood failure test results shall equal or exceed 60% wood failure.

**13.6 SUBSEQUENT QUALIFICATION**

**13.6.1 NEW ITEM**

Separate qualification sampling and testing outlined in Section 13.3 is required for each new item for which a grade stamp is desired.

*Note: New items may include, but are not necessarily limited to, changes in size or species/species group.*

**13.6.2 MAJOR CHANGES**

When a major change and/or process condition (which, in the opinion of the Agency, may affect the quality of the product) occurs, the facility shall immediately notify the Agency.

The qualification procedures outlined in Section 13.2.2 shall be required.

*Note 1: Major changes are production line changes which apply to all items currently being produced. Major changes may include, but are not necessarily limited to, any new adhesive, a change to the joint profile, fingerjoining of green or green-frozen lumber, and changes to the manufacturing flow process.*

*Note 2: Changes in size and/or species or species groups are not considered major changes. Requirements set forth in Section 13.6.1 are intended to deal with size and/or species changes.*

*Note 3: Reversion to a previously qualified adhesive is generally not considered to be a major change, unless considered so in the opinion of the Agency.*

*Note 4: When the major change involves a new adhesive, the Agency may require samples to be obtained from all items, if in the Agency's judgement, the different adhesive application systems, mixing systems or allowance for more extreme gluing conditions warrant an expanded evaluation.*

**13.7 NON-PRODUCTION OF STRUCTURAL FACE-GLUED LUMBER**

When a qualified facility does not produce structural face-glued lumber for a period exceeding one year, all item qualifications for that facility shall become void. The requirements for initial qualification shall be satisfied prior to renewed production of structural face-glued lumber.

**14.0 EQUIPMENT CALIBRATION**

Records of all calibration and spot check verifications shall be maintained for at least 6 years.

**14.1 TEST EQUIPMENT AND SPOT-CHECK DEVICES**

An independent calibration laboratory acceptable to CLSAB, shall calibrate the test equipment and spot-check devices prior to initial qualification and once a year thereafter.

Procedures for calibration of the test equipment shall be consistent with the applicable sections in ASTM E4 and /or other applicable nationally recognized standards acceptable to CLSAB, except that the percentage error shall not exceed  $\pm 2.0\%$ .

*Note: The listed standard and any other test standards and procedures for calibrating measuring devices and equipment must be nationally recognized and acceptable to CLSAB to be deemed applicable.*

It is the responsibility of the facility to maintain the operating condition of its test equipment in accordance with requirements set forth in their QC Manual and this Standard.

The test equipment shall be spot-checked in accordance with procedures set forth in the QC Manual, this Standard, and with the applicable sections in ASTM E4 and/or other applicable nationally recognized standards acceptable to CLSAB.

During production, spot-checks shall be performed at a frequency level listed in Table 3 and whenever there is reason to suspect the equipment may be out of calibration or damaged.

The Agency shall be notified immediately if damage to the test equipment or a spot-check device has occurred.

*Note: Re-calibration of the test equipment or spot-check devices by an independent calibration laboratory may be required by the Agency.*

**TABLE 3 - TEST EQUIPMENT SPOT-CHECK FREQUENCY**

Equipment	Minimum Spot-Check Frequency
Bending Test Equipment	At least once a week
Shear Test Equipment	At least once a week
Other Test Equipment	As per manufacturer's specifications, the Quality Control Manual, or this Standard, whichever period is more frequent.

**14.2 CALIBRATION DEVICES**

The calibration devices used by the independent calibration laboratory shall meet the applicable requirements of ASTM E74 for force-measuring devices and/or other applicable nationally recognized standards acceptable to CLSAB.

### 14.3 INDEPENDENT CALIBRATION LABORATORY REPORTING REQUIREMENTS

The calibration report and certificates from the independent calibration laboratory shall comply with the reporting requirements outlined in ASTM E4 and/or other applicable nationally recognized standards acceptable to CLSAB.

The report from the independent calibration laboratory shall include at least:

- a) Results of the calibration of the sensors of the equipment following applicable sections of ASTM E4, ASTM E74 and/or other nationally recognized standards acceptable to CLSAB,
- b) Description of the method of verification including details of the preloading, if applicable,
- c) Indication if the sensitivity or point of calibration of the test equipment was changed or not,
- d) Information on the Reference calibration devices used by the laboratory including the due date of calibration,
- e) The average target and tolerance values to be used,
- f) A statement that the test equipment is in satisfactory working condition,
- g) Temperature near the test equipment at time of the calibration,
- h) Whether a facility quality control person was present to confirm values, and
- i) Date and location of the calibration.

A copy of the final calibration report shall be forwarded to the Agency.

### 15.0 QUALITY CONTROL REQUIREMENTS

Verification of bonded face quality shall be as follows:

#### 15.1 QUALITY CONTROL PROCEDURES

The quality control procedures described herein are intended to detect non-conformance. The properties being considered are:

- a) Bending strength,
- b) Shear strength parallel to grain, and
- c) Wood failure.

The quality control procedures adopted by the facility shall be fully documented in their Quality Control Manual.

Verification of product quality includes two independent procedures:

- a) One dealing with the quality, strength and resistance to moisture of the structural face-glued lumber bonded surfaces, and

- b) One dealing with the grade of the lumber containing structural face-glued lumber bonded surfaces. Verification of the lumber grades shall follow the grading provisions set forth in the NLGA Standard Grading Rules.

### 15.2 QUALITY CONTROL SAMPLING

#### 15.2.1 SAMPLING METHOD

The random sampling method shall be approved by the Agency and documented in the Quality Control Manual.

Specimens shall be collected from grade stamped production. The sampling method shall include procedures for selecting the structural face-glued lumber specimens for bending and shear strength tests and which portion will be tested for wood failure.

#### 15.2.2 SAMPLING FREQUENCY

Sampling frequency requirements are dependent on the test being carried out as follows:

*Note: Under special circumstances, such as to accommodate the facility's production schedule, the Agency may request the facility to increase its quality control sampling frequency.*

##### 15.2.2.1 BENDING STRENGTH SAMPLING

Bending strength test specimens shall be collected at a rate of **1** specimen per production hour, or part thereof, with no fewer than **5** specimens collected during a production shift of less than 5 hours.

##### 15.2.2.2 SHEAR STRENGTH PARALLEL TO GRAIN and WOOD FAILURE SAMPLING

Shear strength test specimens shall be collected at a rate of **1** per production hour, or part thereof, with no fewer than **5** specimens collected during a production shift of less than 5 hours.

Each specimen shall yield **2** test blocks (located at least 2 feet apart from each other).

Wood failure evaluations shall be determined from the same test blocks.

### 15.3 QUALITY CONTROL TESTING

Testing for bending strength, shear strength parallel to grain and wood failure shall be performed in accordance with the procedures described in Section 9.

### 15.4 ANALYSIS OF QUALITY CONTROL TESTS

All production from a shift, or part thereof, shall be held in inventory pending the results of the quality control evaluation of Sections 6, 7, and 8 of this Standard for that production period.

Test results shall be entered on Agency approved control forms. The control forms shall be designed so that the process properties qualified under Sections 13.3 and 13.5.1 are recorded and “**IN-CONTROL**” and “**OUT-OF-CONTROL**” situations shall be readily detectable.

**15.4.1 IN-CONTROL**

When all of the process properties referred to in Section 15.4 remain “**IN-CONTROL**”, the item from which the quality control samples were drawn shall be deemed to comply with the property requirements of this Standard.

**15.4.2 OUT-OF-CONTROL**

The requirements of this Section relate to the conditions described in APPENDICES VII and VIII.

When any of the process properties described in Section 15.4 becomes “**OUT-OF-CONTROL**”, the item from which the quality control samples were drawn shall be held pending results of the following tests (as applicable):

- a) An examination of the test procedures, calibration and/or calculations shall be made to determine whether there were errors.
- b) If no such errors are identified, proceed to Section 15.4.2.1.
- c) Held production deemed to be “**OUT-OF-CONTROL**” after evaluations in accordance with Section 15.4.2.1 shall be rejected. The grade stamps shall be obliterated or removed.

**15.4.2.1 BENDING STRENGTH, SHEAR STRENGTH PARALLEL TO GRAIN AND/OR WOOD FAILURE**

When the production represented by a specific time frame from which the quality control sample was drawn fails to meet the bending strength, shear strength or wood failure requirements prescribed in Sections 8.1, 8.2, and 8.3, production from this time frame shall be held pending the results of a **28**-specimen bending test sample or the results of **14**-specimen shear strength/wood failure test sample (yielding 28 test blocks), for whichever of the test(s) that went “**OUT OF CONTROL**”.

These confirmation samples shall be randomly selected and tested in accordance with Section 13.4.

- a) **BENDING STRENGTH:** When the test results for MOR fail to meet requirements of Section 13.5.2.1, the held item shall be deemed to be in non-compliance with the requirements of this Standard and all grade stamps shall be obliterated from the structural face-glued lumber.

- b) **SHEAR STRENGTH PARALLEL TO GRAIN:** When test results indicate the process is “**IN-CONTROL**” for shear strength, the facility shall proceed to Section 15.4.2.1 c) for wood failure evaluation.

When the test results for shear strength fail to meet the requirements of Section 13.5.2.2, the held item shall be deemed to be in non-compliance with the requirements of this Standard and all grade stamps shall be obliterated from the structural face-glued lumber.

- c) **WOOD FAILURE:** When shear test results indicate the process is “**IN-CONTROL**” and the wood failure test results confirm that the “**IN-CONTROL**” requirements have been regained, the held item shall be deemed to comply with the wood failure requirements of this Standard.

When the test results for wood failure fail to meet requirements of Section 13.5.2.3, the held item shall be deemed to be in non-compliance with the requirements of this Standard and all grade stamps shall be obliterated from the structural face-glued lumber.

*Note: The Agency may request a facility to hold the wood failure test specimens for examination.*

**15.5 IDENTIFICATION AND TRACEABILITY**

Each package of structural face-glued lumber leaving the facility production line shall be identified with the time and date it left the production line.

*Note: This requirement is to allow for traceability of an item if further testing is required or in the event of a non-conformance or an “**OUT-OF-CONTROL**” condition.*

**15.6 QUALITY CONTROL RECORDS**

Facility control records shall include:

- a) Test equipment calibration, spot-check, and maintenance records,
- b) Quality control test data, and
- c) All structural face-glued lumber production stoppages as a result of quality control requirements and reports of the corrective actions taken.

Separate records shall be maintained for each item produced.

All records shall include the date when performed and shall be retained for at least 6 years. These records shall be made available to the Agency upon request.

## 16.0 REINSPECTION PROVISIONS

### 16.1 GENERAL

Response to complaints on structural face-glued lumber involving visual grade, size, moisture content, tally, bondline strength or assigned design values, shall be based on the applicable requirements within this section of the Standard, and by the requirements set forth in NLGA Para. 400.

Sample selection and testing for reinspection shall be performed by the Agency whose logo appears on the lumber (or by an independent accredited testing organization approved by the original grading Agency). Only certified test equipment calibrated to a national standard and using a process mutually agreed upon by the Agency, the seller, and the buyer shall be used.

### 16.2 BENDING STRENGTH AND/OR SHEAR STRENGTH PARALLEL TO GRAIN SAMPLING AND EVALUATION

In the case of a dispute pertaining to bending strength or shear strength parallel to grain or assigned design values, a random sample of the item under complaint shall be obtained as follows:

- a) **80** specimens for the bending MOR property evaluation to be tested in accordance with Section 9.1 of this Standard in such a way that the compression face is randomly generated, and/or
- b) **80** specimens for the shear strength parallel to grain (Fv) evaluation to be tested in accordance with Section 9.2 of this Standard.



Testing shall be undertaken in accordance with procedures set forth in Section 9.1 and 9.2 of this Standard using test equipment calibrated to a national standard and certified by an independent calibration laboratory.

Test results of the lumber in dispute shall be assessed as follows:



- a) For the bending MOR, not more than **6** specimens out of **80** shall have an MOR value that is less than the corresponding MOR test value for the size, grade, and species group as provided in Table 2.
- b) For the shear strength parallel to grain, not more than **6** specimens out of **80** shall have a shear strength parallel to grain value that is less than the corresponding Fv test value for the species group as provided in Table 2.

## APPENDICES (INFORMATIVE)

### APPENDIX I – EXAMPLES OF LUMBER CROSS-SECTIONS FALLING WITHIN THE SCOPE OF SPS 6

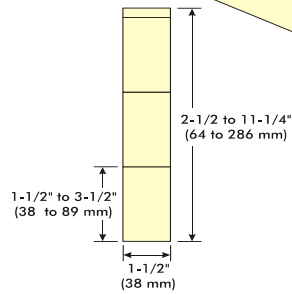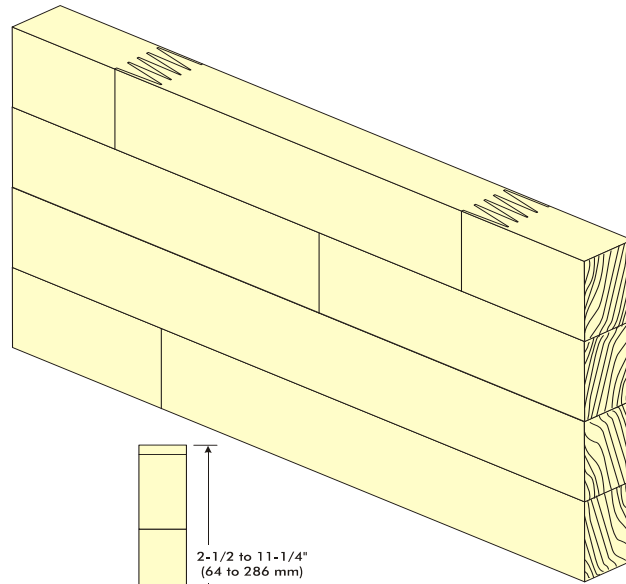

G-584

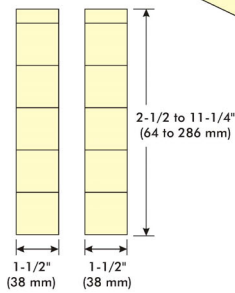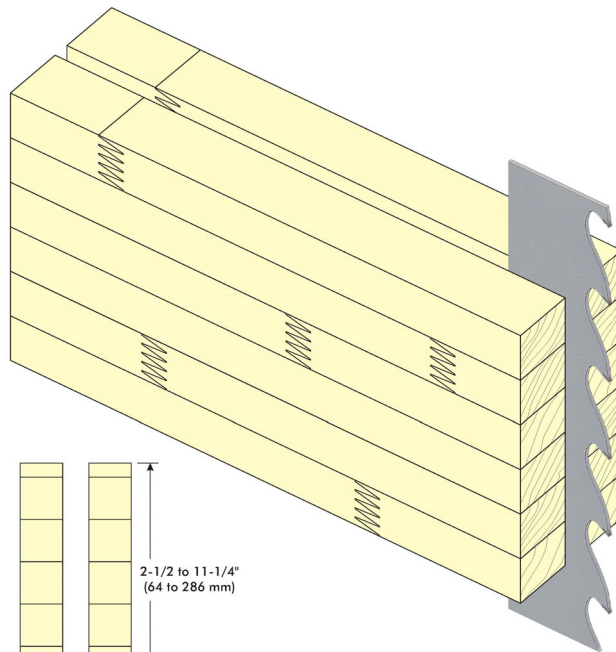

G-584

FIGURE 1 - EXAMPLES OF STRUCTURAL FACE-GLUED LUMBER PRODUCT CROSS-SECTIONS

**APPENDIX II – MOR SPAN-TO-DEPTH ADJUSTMENT FACTORS**


In cases where the length of the test specimen is such that only a span to depth ratio of less than 21 is possible, the following correction factors shall be applied to the MOR test value shown in Table 2.

**TABLE 4 - CORRECTION FACTORS FOR EDGE BENDING MOR**

Span to Depth Ratio	Multiply MOR Value by: <sup>(1)</sup>
20	1.0069
18	1.0218
17	1.0300
16	1.0388
15	1.0482
14	1.0584
13	1.0694
12	1.0815
11	1.0948
10	1.1095

<sup>(1)</sup> Values adapted from ASTM D1990. Alternatively, the multiplier k may be calculated from the following equation:  
 $k = 21^{0.14} S^{-0.14}$  where, S = span-to-depth ratio used

**APPENDIX III – SHEAR BLOCK TEST SPECIMEN DIMENSIONS**

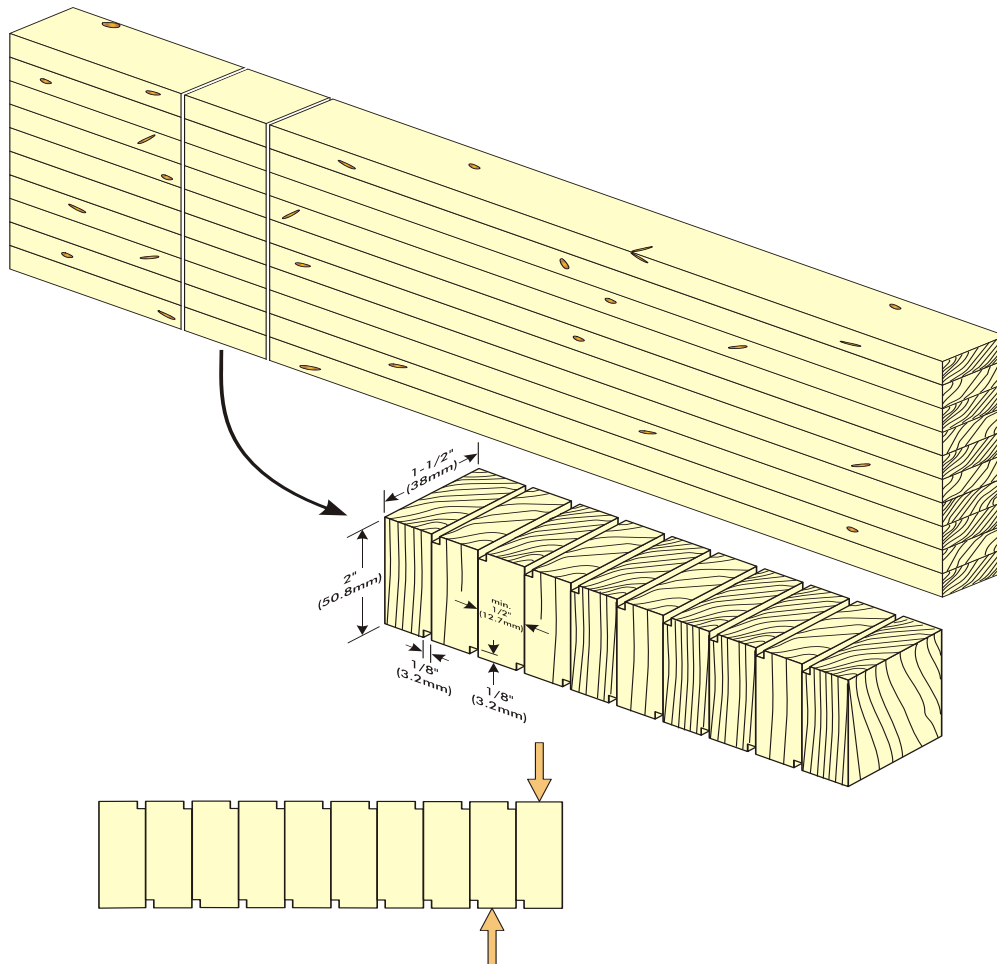

G-584

**FIGURE 2 - TEST SPECIMEN SHEAR BLOCK AND SAW KERF DIMENSIONS**

#### APPENDIX IV – PRESSURE-VACUUM-DRY TREATMENT

Specimens are subjected to the following pressure-vacuum-dry treatment, which is a modification of Method B of ASTM D1101.

##### Procedures

If the initial moisture content of the test specimens is 20% or more, dry the specimens using air at a temperature of  $160^{\circ}\text{F} \pm 5^{\circ}$  ( $71^{\circ}\text{C} \pm 3^{\circ}$ ) to an initial moisture content of 19% or less.

Place the test specimens in the pressure vessel and weight them down. Admit sufficient water at a temperature of 65 to 85°F (18.3 to 29.4°C), so that the test specimens are completely submerged.

Separate the test specimens by stickering, wire screens or other means so that all end grain surfaces are freely exposed to water.

Draw a vacuum of 20 to 25 inches (508 to 635 mm) of mercury and hold it for 30 minutes, then release the vacuum and apply a pressure of  $75 \pm 5$  psi ( $0.520 \pm 0.034$  MPa) for a period of two hours.

Dry the test specimens using air at a temperature of  $160^{\circ}\text{F} \pm 5^{\circ}$  ( $71^{\circ}\text{C} \pm 3^{\circ}$ ). The air circulation and number of specimens in the oven at any time shall be selected such that the specimens are dried to moisture content of 19% or less.

During drying, place the specimens at least 2 inches (50 mm) apart, with the end grain surfaces and bonded face orientation parallel to the direction of airflow.

Dry the specimens until the moisture content of each specimen has reached 19% or less.

#### APPENDIX V – COMMENTARY ON QUALITY CONTROL MANUAL CONTENTS

The Quality Control (QC) Manual specifies, in writing, one or more sets of facility operating conditions that are known to result in a product that is in continuous conformance with the requirements of this Standard. The qualification applies only to product(s) produced within the specified limits of the QC Manual.

The details of the QC Manual will vary with the process used. Some aspects of it may be common to all lumber sizes and species combinations, while other aspects may vary with size and species. The QC Manual provides details of all test procedures used, the wood failure criteria used, and the records to be kept of in-process checks that are made.

The QC Manual describes the manufacturing operation, broken down by station. For each station in the sequence of manufacture, a description is required of the function performed by the equipment, the skills the operator requires, the responsibility of the operator in charge of that station, and (if required) what checks are instituted to ensure that the equipment and operator are performing within the desired limits.

Procedures must be outlined for the absence of any operator with specialized skills essential to the process.

Examples of typical stations are:

**Input grading:** station where defects are removed from the ends of the lumber prior to machining of the fingerjoint (if applicable),

**Machining of the fingerjoints (if applicable) and the bonded surface:** station where set-up tolerances are monitored and where cutter heads are changed,

**Glue mixing:** station concerned with ensuring the prescribed proportions of adhesive and hardener are thoroughly blended at the prescribed temperature levels,

**Make-up station(s):** fingerjoining station (if applicable) consisting of top dead rolls mounted above the in-feed table (ahead of the crowder and retard system) which assists the operator with assembly of the joint. Face-gluing station where glue is applied to component surfaces.

**Off-line QC test equipment:** station where quality control specimens are tested.

The QC Manual should include special provisions for the shut-down and start-up of the gluing line, particularly during temporary stoppages. The latter is particularly significant in preheat processes, in which the glue may be spread on heated wood and must be put under gluing pressure within a limited time to avoid pre-cure of the glue.

#### APPENDIX VI – COMMENTARY ON WOOD FAILURE ASSESSMENT

In this Standard, wood failure means that the face-glued surface fails in a shallow layer of wood next to the bondline. The significance of wood failure is that it correlates inversely with delamination resistance. If a high degree of wood failure develops, the face-glued bondline should be resistant to delamination. Conversely, any area in the face-glued bondline that shows no wood failure may be prone to delaminating.

Wood failure assessment is a mandatory requirement of this Standard.

Trained personnel should be able to read single blocks from a standard set with a reproducibility of  $\pm 15\%$  and be within  $\pm 5\%$  of the average for the set.

APPENDIX VII – FLOW CHART FOR “OUT-OF-CONTROL” IN BENDING STRENGTH

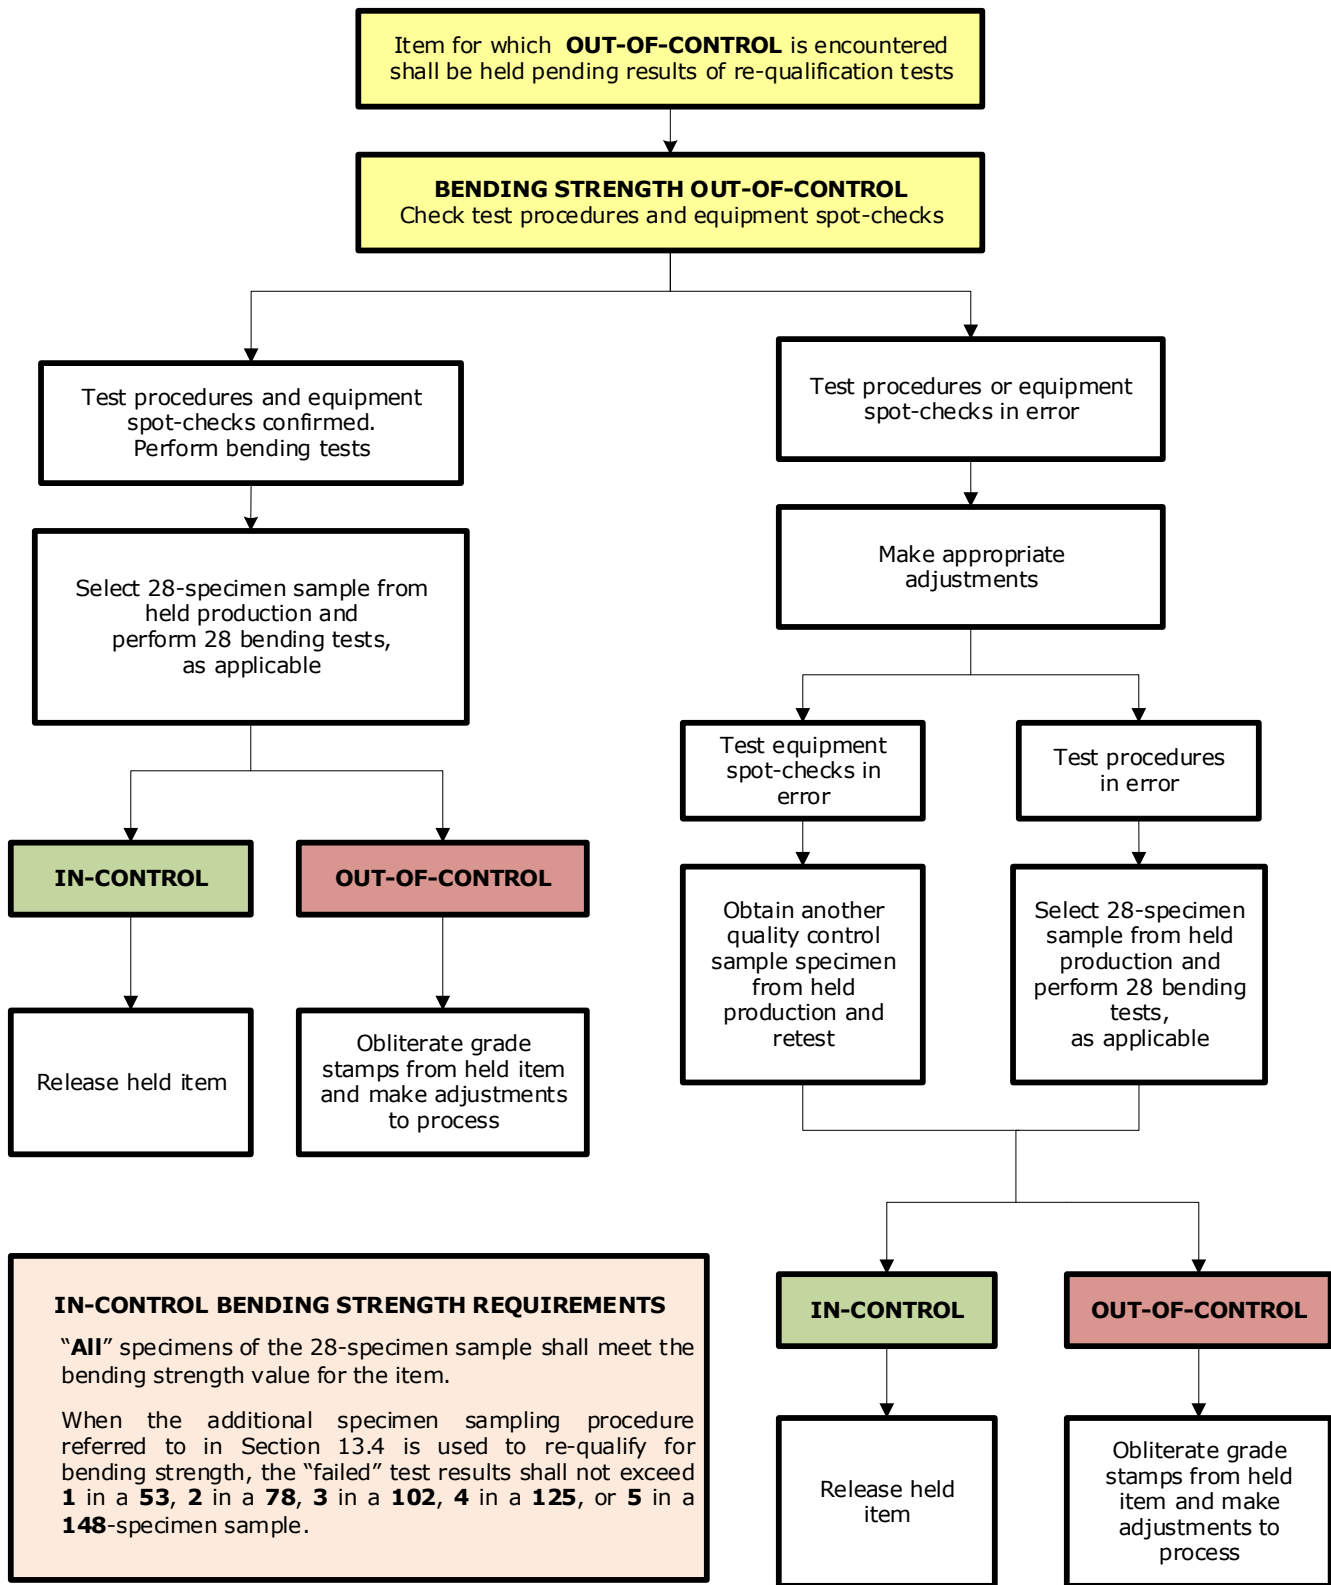


FIGURE 3 - BENDING STRENGTH FAILURE RE-QUALIFICATION FLOW CHART

APPENDIX VIII – FLOW CHART FOR “OUT-OF-CONTROL” IN SHEAR STRENGTH PARALLEL TO GRAIN AND/OR WOOD FAILURE

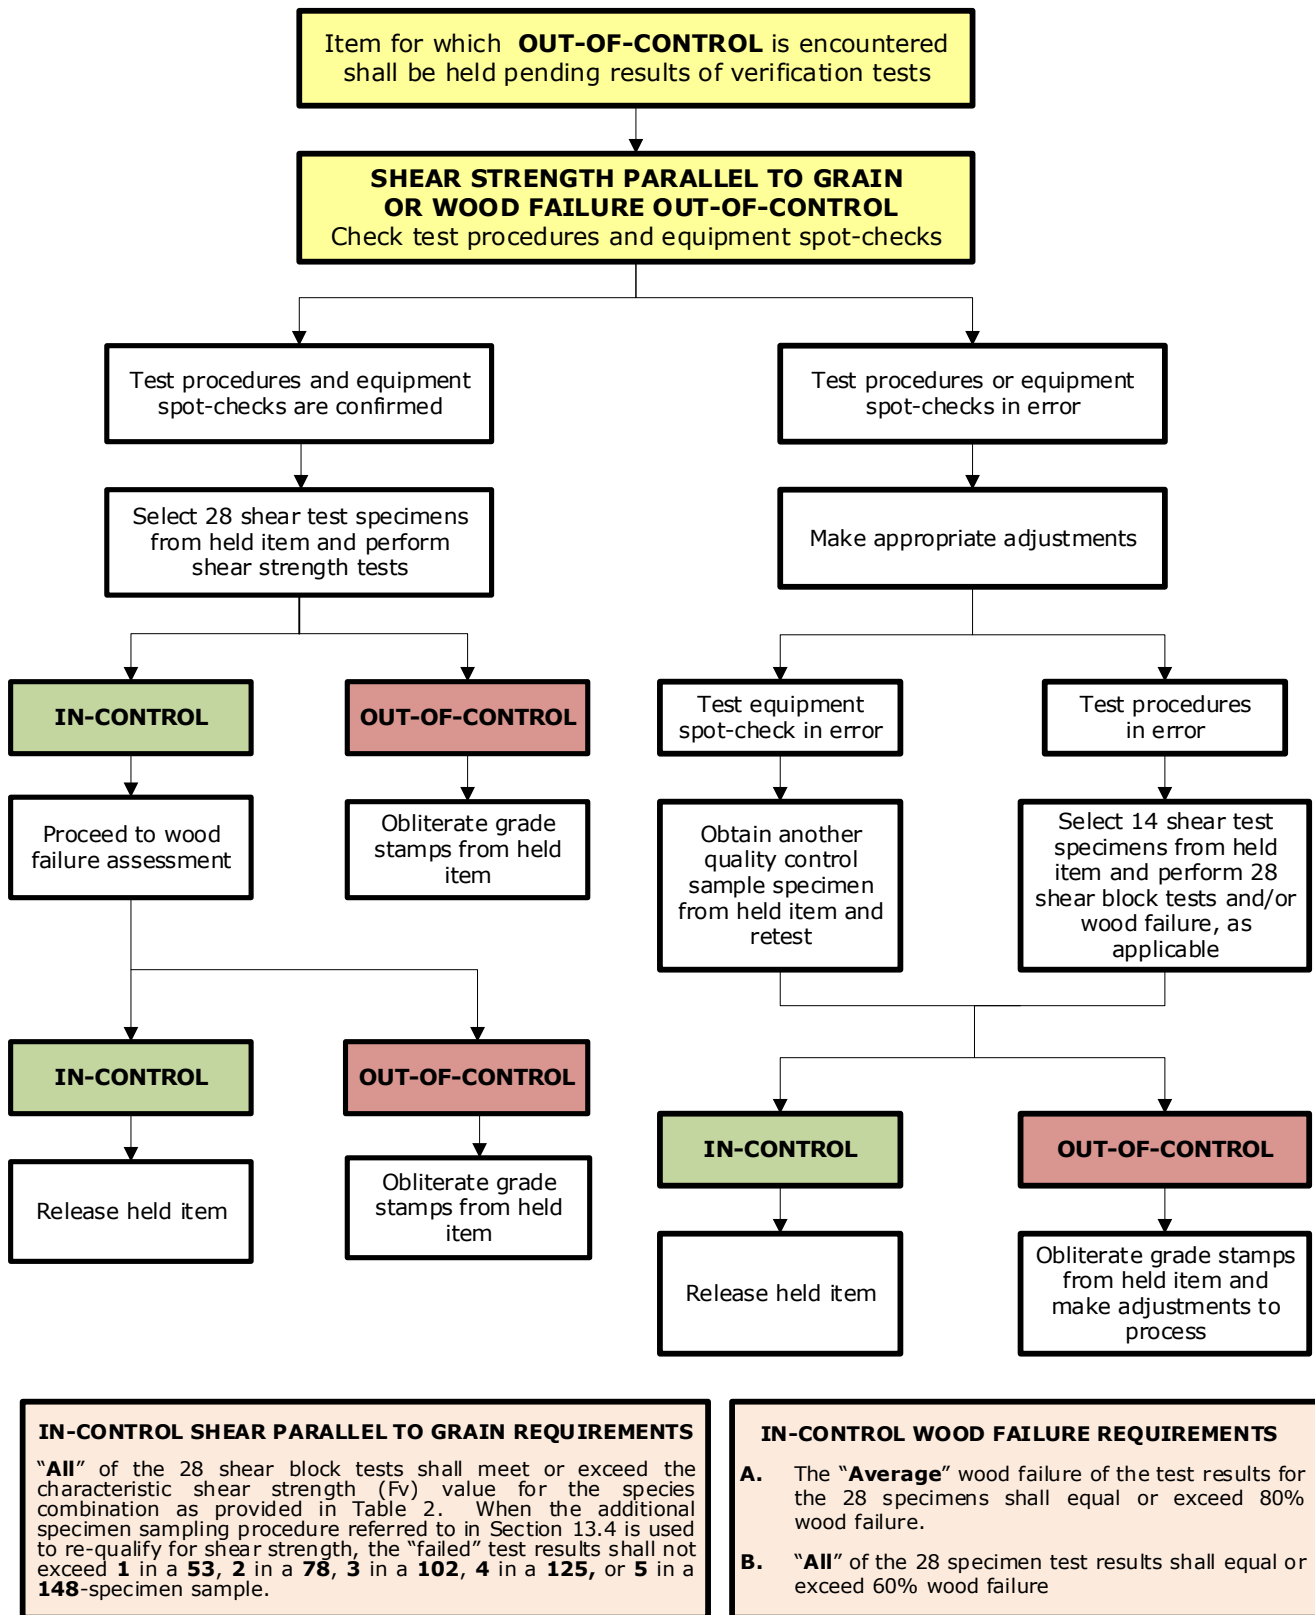


FIGURE 4 - SHEAR STRENGTH PARALLEL TO GRAIN AND/OR WOOD FAILURE RE-QUALIFICATION FLOW CHART

**APPENDIX IX – AGENCY ADMINISTRATION**

The accredited Agency is required to administer this Standard at a manufacturing facility. Agency approval of a facility to grade stamp structural face-glued lumber must be contingent upon the facility's compliance with the procedures and requirements of this Standard.

Agency inspections should include, at a minimum, reporting on the following:

- a) Examination of production samples from the facility's inventory, the facility's records, and procedures, to verify compliance to the requirements of **Part A** of this Standard and the QC Manual.
- b) Examination of the bending and shear test equipment including observations on:
  - i) wear and damage,
  - ii) lubrication and operations of moveable parts, and
  - iii) record of weekly calibration
- c) Examination of the pressure-vacuum-dry treatment equipment, including the apparatus for measuring temperature, pressure and time, and the drying chamber.
- d) Inspection of the glue mixing equipment and procedures, including the accuracy of the weighing equipment, mixing proportions, and cleanliness of the facility.
- e) Verification of the wood failure measurement and procedures.
- f) Examination of the control system used to prevent overheating of the wood on the gluing surfaces.

## NLGA - SPS 6

May 1, 2026

---

This NLGA Special Products Standard for Structural Face-Glued Lumber (**SPS 6**) consists of 29 pages.

This Standard, like all NLGA Standards, is subject to periodic review and may be amended from time to time.

To identify or obtain the most current version of NLGA – SPS 6, or any associated Supplements or Errata, check the publication section of the NLGA website at [www.nlga.org](http://www.nlga.org).